

Lawrence Berkeley National Laboratory

Recent Work

Title

Magnetic Field Enhanced Superconductivity in Epitaxial Thin Film WTe_2 .

Permalink

<https://escholarship.org/uc/item/1642v6qf>

Journal

Scientific reports, 8(1)

ISSN

2045-2322

Authors

Asaba, Tomoya
Wang, Yongjie
Li, Gang
et al.

Publication Date

2018-04-01

DOI

10.1038/s41598-018-24736-x

Peer reviewed

SCIENTIFIC REPORTS

OPEN

Magnetic Field Enhanced Superconductivity in Epitaxial Thin Film WTe_2

Tomoya Asaba¹, Yongjie Wang², Gang Li¹, Ziji Xiang¹, Colin Tinsman¹, Lu Chen¹, Shangnan Zhou¹, Songrui Zhao², David Laleyan², Yi Li³, Zetian Mi² & Lu Li¹

In conventional superconductors an external magnetic field generally suppresses superconductivity. This results from a simple thermodynamic competition of the superconducting and magnetic free energies. In this study, we report the unconventional features in the superconducting epitaxial thin film tungsten telluride (WTe_2). Measuring the electrical transport properties of Molecular Beam Epitaxy (MBE) grown WTe_2 thin films with a high precision rotation stage, we map the upper critical field H_{c2} at different temperatures T . We observe the superconducting transition temperature T_c is enhanced by in-plane magnetic fields. The upper critical field H_{c2} is observed to establish an unconventional non-monotonic dependence on temperature. We suggest that this unconventional feature is due to the lifting of inversion symmetry, which leads to the enhancement of H_{c2} in Ising superconductors.

Superconductivity generally competes with magnetic fields. Based on thermodynamics, an applied magnetic field usually suppresses superconductivity by destroying the underlying electron pairing in the superconducting state¹. This pair breaking principle has been confirmed in thousands of superconductors. However, this simple principle may be invalid when strong spin-orbit-coupling or symmetry protection brings novel physics to bear on the superconducting state². As a result, the superconducting transition temperature (T_c) is expected to be enhanced by magnetic fields in the finite momentum pairing system with strong Rashba-type spin orbit coupling³, non-centrosymmetric superconductors⁴, in topological superconductors⁵, and notably in the unconventional Ising superconductors based on atomic layered transition metal dichalcogenides (TMD)⁶. In particular monolayered TMD hosts unique valley and spin degrees of freedom, which leads to a number of novel phenomena^{7–16} due to their unique non-centrosymmetric crystal structure. The unique lifting of the inversion symmetry leads to Ising superconductivity in MoS_2 and NbSe_2 ^{6,15–19}, which have an upper critical field H_{c2} as high as 5 to 10 times larger than the paramagnetic Pauli limit H_p . The notable prediction of the theory underlying Ising superconductivity is the non-monotonic temperature (T) dependence of H_{c2} in the ground state⁶ due to the competition between Ising and Rashba type spin-orbit coupling. The former interaction enhances the superconductivity while the latter suppresses superconductivity. Thus, TMD materials are expected to show both non-monotonic H_{c2} predicted at low temperature and T_c enhancement by the magnetic field due to the non-centrosymmetric crystal structure. However, while high H_{c2}/H_p has been observed in MoS_2 and NbSe_2 , neither non-monotonic H_{c2} nor T_c enhancement by magnetic field has been observed so far. Therefore, direct observation of these features is important to understand the Ising superconductivity. Furthermore, both MoS_2 and NbSe_2 have the hexagonal 2H crystal structure, and the system becomes non-centrosymmetric only when the thin film consists of odd atomic layers. It is still unknown if Ising pairing can exist in a different crystal structure, especially when the bulk crystal itself is non-centrosymmetric.

The best candidate to search for non-centrosymmetric Ising superconductivity is superconducting tungsten telluride (WTe_2). Many unique topological phases are predicted in this family of TMDs, such as quantum spin Hall effect in the monolayered WTe_2 film²⁰, and type-II Weyl semimetal in MoTe_2 and WTe_2 ²¹. The type-II Weyl state was further confirmed by a number of photoemission studies in both Te-based TMD materials and in related materials^{22–28}. These features are deeply connected to its unique T_d crystal structure, the bulk non-centrosymmetric structure. Furthermore, a giant magnetoresistance was also observed in WTe_2 ²⁹. A

¹Department of Physics, University of Michigan, Ann Arbor, MI, 48109, USA. ²Department of Electrical and Computer Engineering, McGill University, Montreal, Quebec, H3A 0E9, Canada. ³Department of Physics and Astronomy, Johns Hopkins University, Baltimore, MA, USA. Tomoya Asaba and Yongjie Wang contributed equally to this work. Correspondence and requests for materials should be addressed to L.L. (email: luli@umich.edu)

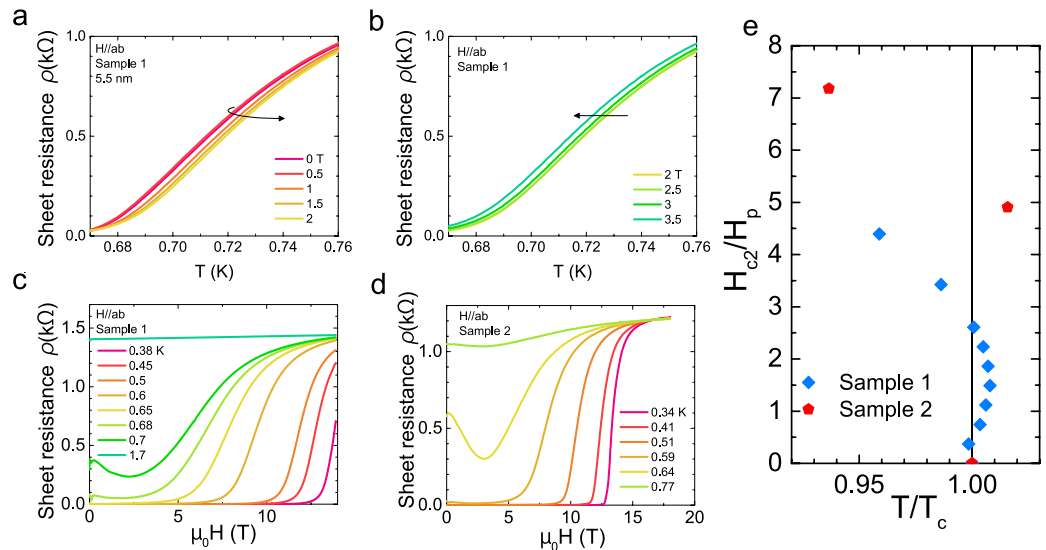


Figure 1. Field-induced enhancement of T_c at low in-plane field and high temperature. **(a,b)** The temperature dependence of the 5.5 nm WTe_2 Sample 1 (T_c 0.71 K) film sheet resistance, ρ , at fixed fields. The black arrow marks the direction of the increase of in-plane magnetic fields. In Panel a, the superconducting transition shifts to higher T as the in-plane field increases to 2 T, whereas at higher field, the transition shifts to lower T . Combining panel a and b shows the transition temperature T_c gets enhanced at the finite in-plane magnetic field. **(c)** The magnetic field H dependence of 5.5 nm WTe_2 film Sample 1. At around T_c , this sample shows strong negative magnetoresistance. **(d)** Similar negative magnetic field H dependence of R is observed in 5.5 nm WTe_2 film Sample 2 (T_c 0.64 K). **(e)** The temperature dependence of in-plane upper critical field for 5.5 nm WTe_2 thin film around $T = T_c$. Field-induced enhancement of T_c shows a maximum of 0.8% in sample 1 ($H_p = 1.31$ T) and 1.6% in sample 2 ($H_p = 1.21$ T).

superconducting state has been observed under high pressure in WTe_2 ^{30,31} and in ambient pressure in MoTe_2 ³². The interplay between the type-II semimetal phase and superconductivity could give rise to many unconventional features. In this letter, we not only observed the highest H_{c2}/H_p (10) in TMD materials, but also discovered two unique unconventional features in superconducting WTe_2 thin films — the magnetic-field-enhancement of superconductivity and non-monotonic H_{c2} as a function of temperature.

To study the ground state superconducting pairing requires the growth of thin films. The film thickness provides a geometrical constraint that is smaller in our thin-film samples than the bulk coherence length. This removes the orbital effects of an in-plane magnetic field that would otherwise suppress the superconductivity in the bulk, thereby realizing the novel conditions for Ising superconductivity. This has been demonstrated by the observation of 2D Ising superconductivity in mechanically exfoliated NbSe_2 and MoS_2 ^{6,15–19}, showing high H_{c2}/H_p . However, TMD monolayered devices are realized by pioneering work in thinning layered TMD materials into single atomic layers using mechanical exfoliation⁷, chemical vapor deposition³³, and epitaxial growth^{34–37}. The mechanical exfoliated WTe_2 or MoTe_2 devices are generally micron sized and their electronic mobility in the monolayer limit is generally too low to host an interesting ground state. In our paper, we report the first Molecular Beam Epitaxy (MBE) growth of thin WTe_2 films.

Results

Thin films of WTe_2 with a thickness of 5.5, 7, 10 and 14 nm were grown on $c\text{-Al}_2\text{O}_3$ (0001) substrate using a Veeco Genxplor MBE growth system (see the supplement). The scanning probe microscopy (SPM) image of the WTe_2 film exhibits smooth and continuous surface morphology. The surface roughness is estimated to be ~ 0.22 nm, without the presence of any sharp edges, wrinkles, or discontinuities. The stoichiometric analysis was performed by high-resolution X-ray photoelectron spectroscopy immediately after growth. The shape and position of the core-level W-4d and Te-3d peaks are consistent with previous studies of WTe_2 crystal structures^{35,38}. The presence of W and Te oxidation peaks were not observed, confirming the high purity of epitaxial WTe_2 thin films. The ratio of W and Te was measured to be 1:1.93, suggesting the formation of nearly stoichiometric WTe_2 . They were uniformly formed on a sapphire substrate with precise thickness control. We observed two-dimensional superconductivity in the ground state and a Berezinskii-Kosterlitz-Thouless (BKT) transition (see the supplement).

The resistivity data of 5.5 nm WTe_2 films at around the critical temperature is shown in Fig. 1. Specifically, Fig. 1(a) and (b) give the resistivity data from sample 1 as a function of temperature at the fixed magnetic field around critical temperature. The T_c clearly increases with magnetic field up to 2 T (Fig. 1(a)), then starts to decrease with higher field (Fig. 1(b)). The T_c enhancement is about 10 mK at 2 T. Even larger magnetic-field-enhancement of T_c was observed in other samples, as shown in Fig. 1(e) for Sample 2, corresponding to 1.6% enhancement. The large negative magnetoresistance around T_c is connected to the observed enhancement of T_c as shown in Fig. 1(c) and (d). Thicker samples also show similar negative magnetoresistance at around T_c (see supplement). Figure 1(e) shows a phase diagram of H_{c2} versus T/T_c for two 5.5 nm WTe_2 thin film samples around $T = T_c$ with the magnetic field

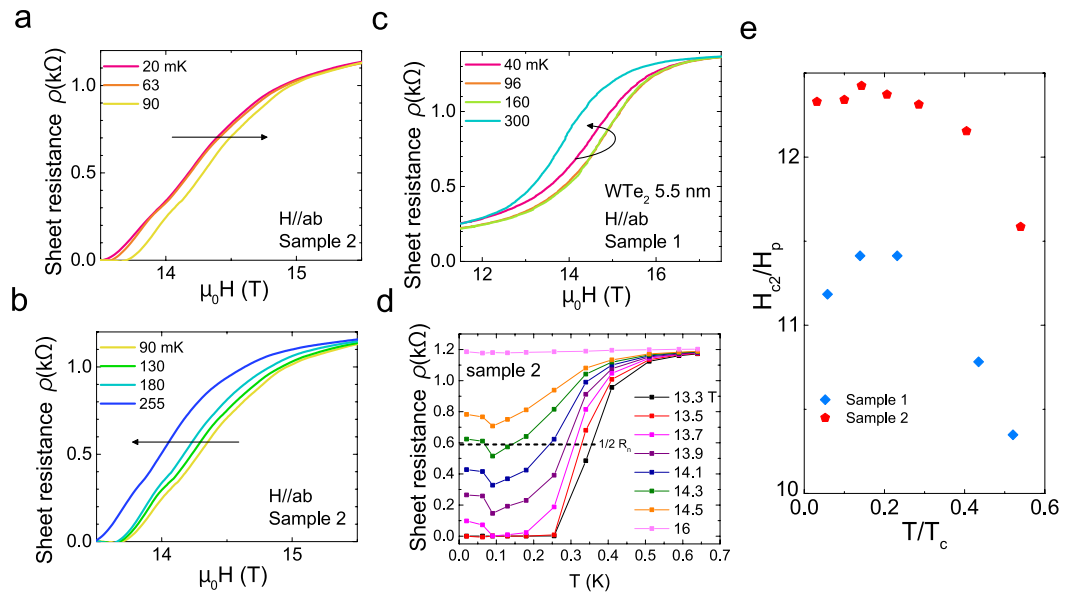


Figure 2. Field-induced enhancement of T_c at high in-plane field and low temperature. **(a,b)** Sheet resistance of the 5.5 nm thick WTe₂ film (Sample 2). The black arrow marks the direction of increasing temperature. Similar non-monotonic behavior is confirmed in Sample 2. **(c)** Sheet resistance of the 5.5 nm thick WTe₂ film (Sample 1) with H parallel to the film ab -plane. As shown by the black arrow marking the direction of increasing temperature, the upper critical field H_{c2} increases first and decreases at warmer T , which indicates the non-monotonic temperature T dependence of H_{c2} . **(d)** At finite in-plane fields close and below H_{c2} , the R vs. T of WTe₂ Sample 2 shows a non-monotonic behavior, indicating the re-entrance of the superconducting state from $0.1 < T < 0.2$ K in the $H = 13.7$ T trace. The dashed line shows the half value of the normal state resistance. As explained in the Method part, this value is used to determine H_{c2} at fixed T , or T_c at fixed H . **(e)** The temperature dependence of in-plane upper critical field for 5.5 nm WTe₂ thin film around zero temperature. Both of samples show a drop of H_{c2} (2% for sample 1, 0.8% for sample 2) as T goes to zero.

applied in-plane. For sample 1, the H_{c2}/H_p vs T/T_c clearly shows the enhancement of T_c with increasing magnetic field. Sample 2 shows a larger enhancement of 1.6% at 3 T. The difference of enhancement between samples may originate from the thickness difference due to the 10% error of our thickness measurement. As shown later, T_c of sample 2 (0.64 K) is lower than that of sample 1 (~ 0.71 K), indicating slightly thinner film thickness.

For comparison, H_{c2} is normalized by Pauli limit H_p . In a BCS superconductor, the Pauli paramagnetic limit (H_p) is the magnetic field value where the paramagnetic Zeeman energy is the same as the superconducting condensation energy. This limit generally is the upper bound for the in-plane H_{c2} because there are no orbital degrees of freedom in a two-dimensional system, so only the spins should determine the superconducting property^{39,40}. In the weakly coupled limit, the BCS superconductor condensation energy is $3.52k_B T_c$. Thus in units of tesla $\mu_0 H_p = 1.84 * T_c$ where T_c has units of Kelvin¹. Moreover, in the high field normal state R becomes almost constant within the measurement noise limit (see also supplement). Thus, we define the upper critical field H_{c2} as 50% of the constant resistivity value at high fields).

Note that the smaller resistivity at finite fields is not due to the negative magnetoresistance from the normal state, but rather the enhancement of superconductivity. First, since the magnetic field is applied in-plane, there should be no traditional magnetoresistance effect. The next possibility is the chiral anomaly effect. However, this behavior was observed even when the current direction was perpendicular to the magnetic field, excluding the possibility of a chiral anomaly. This excludes the possibility of the current jetting as well, since it has the similar angular dependence to the chiral anomaly⁴¹. Furthermore, at a temperature slightly above T_c , negative magnetoresistance is no longer observed. Instead, there is small positive magnetoresistance ($\sim 1\%$) at low fields that becomes almost constant at high fields. Thus, the negative magnetoresistance should be understood as the enhancement of superconductivity by the magnetic field.

Another unconventional feature is a non-monotonic behavior of H_{c2} vs T in the zero temperature limit. Figure 2 shows detailed data of the resistivity as a function of in-plane magnetic field and temperature at high fields. In Fig. 2(a), the H_{c2} from sample 1 at 96 mK and 160 mK is 0.29 T higher than that at 40 mK, then drops by 0.8 T at 300 mK. This non-monotonic behavior is more clear in sample 2. In Fig. 2(b), from 20 mK to 90 mK H_{c2} monotonically increases with temperature and reaches a maximum at 90 mK with H_{c2} 0.11 T higher than at base temperature. Above 90 mK, H_{c2} decreases monotonically with temperature, as shown in Fig. 2(c).

The non-monotonic behavior of H_{c2} vs T could be clearly seen in resistivity vs temperature plot at fixed fields from sample 2 shown in Fig. 2(d). At low field such as $H = 13.5$ T, the $R - T$ curve shows a typically superconducting transition from a zero-resistance state at $T = 0$ to a finite normal state resistance at $T = T_c$. As H increases, however, an unconventional feature appears. As shown for the 13.7 T curve, the sample is resistive at $T = 0$, becomes

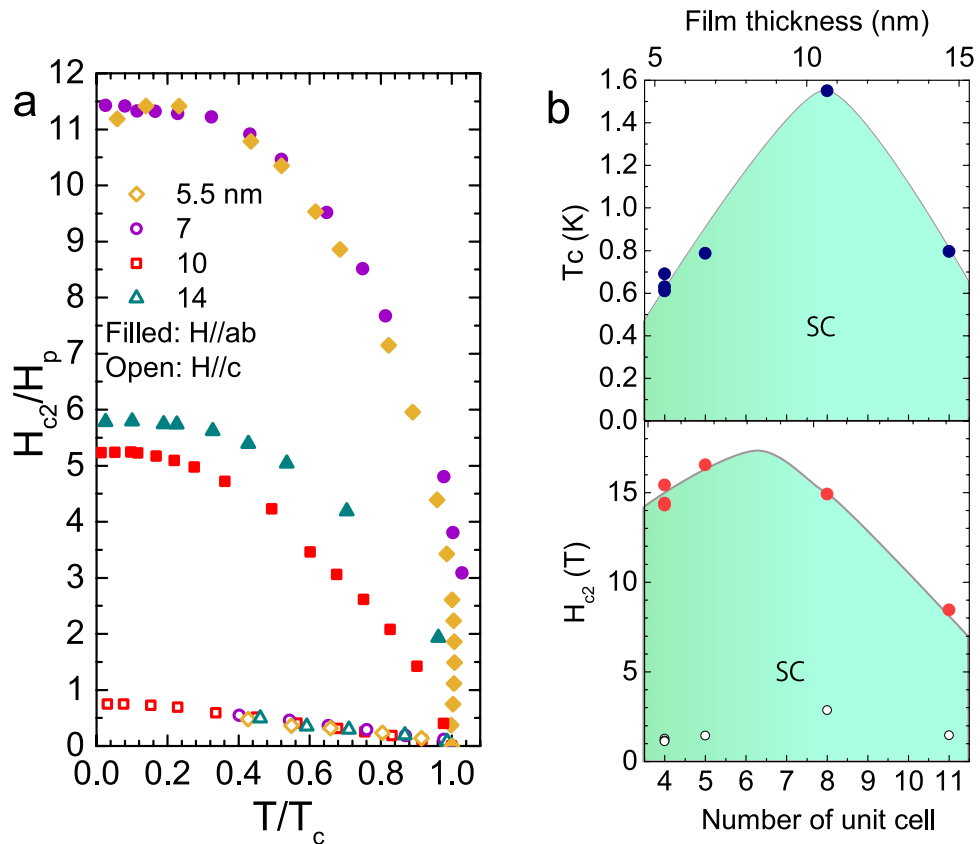


Figure 3. Thickness dependence of upper critical field and critical temperature. (a) Temperature dependence of critical field $H_{c2||ab}$ and $H_{c2||c}$ for 5.5, 7, 10 and 14 nm samples. The T_c values are normalized by the zero field transition temperature T_{c0} . The H_{c2} values are normalized by the paramagnetic Pauli limit $\mu_0 H_p = 1.84 T_{c0}$. (b) The thickness dependence of the superconducting transition temperature (top) and the in-plane upper critical field $H_{c2||ab}$ (red circle) as well as the Pauli limit H_p (black circle) (bottom) at base temperature $T = 20$ mK. The solid lines are drawn for guidance to eye.

non-resistive as T goes close to 100 mK, and eventually comes back to the resistive normal state at $T = T_c$. This behavior demonstrates a re-entrance of the superconducting state at finite T under an in-plane magnetic field.

The evolution of this re-entrance behavior leads to the non-monotonic T dependence of H_{c2} . At 14.3 T the curve crosses the 50% of resistivity in the normal state, indicating the non-monotonic T dependence of H_{c2} .

Figure 2(e) summarizes this unconventional behavior as H_{c2} of both samples flattens out as the temperature approaches zero then drops slightly at around 0 K. For sample 1, H_{c2}/H_p enhancement reaches a maximum of 2% at 96 mK. For sample 2, H_{c2}/H_p is 0.8% higher at 90 mK than at the base temperature (20 mK). This non-monotonic behavior indicates that the enhancement of H_{c2} is due to the temperature. This is the first time that field-induced enhancement of superconductivity has been observed at both zero temperature and T_{c0} .

We point out that the non-monotonic behavior of H_{c2} vs T_c is intrinsic and does not originate from an artificial effect. First, during the measurement the samples are immersed in the He3/He4 superfluid mixture in a dilution refrigerator. This eliminates the possibility of an error arising from a temperature inhomogeneity across the samples. Second, since the in-plane H_{c2} from the thin film would be very sensitive to a field misalignment, it is necessary to adjust the angle carefully before each field sweep. Even the thermal expansion of the system could change the angle enough to affect the measurement. Thus, during the measurement at low temperature, field orientation is aligned within 0.05 degrees to the film plane at each temperature to eliminate the possibility of an angle misalignment. For each curve, the magnetic field was swept up and down to confirm that there is no angle misalignment induced during the measurement. Also, we confirmed that the magnetoresistance curves from field up-sweep and down-sweep overlap each other at each temperature. This indicates that there is no significant instability over time during the data acquisition. Furthermore, at high temperature, a field-calibrated thermometer was used to ensure that the non-monotonic behavior was not simply an artifact of the thermometer's magnetoresistance. Thus, we conclude that the non-monotonic behavior is intrinsic.

Finally, the thickness dependence of critical field and critical temperature is measured for thicker samples. The T dependence of $H_{c2}(T)$ (normalized by the paramagnetic limit H_p) with $H||ab$ direction for 5.5, 7, 10 and 14 nm samples is plotted in Fig. 3(a). As seen in the phase diagram, for 5.5 nm and 7 nm samples H_{c2} is more than ten times larger than the Pauli limit which is greater than any other material except for triplet and non-centrosymmetric superconductors. For the 7 nm sample, in-plane H_{c2}/H_p is higher than eleven, similar to 5.5 nm sample. However, the 10 nm and 14 nm samples show much smaller H_{c2}/H_p , though they still exceed Pauli

limit by far. On the other hand, when the magnetic field is applied parallel to c -axis, all H_{c2} curves overlap with each other and flatten out below Pauli limit H_p . This suggests that H_{c2} is determined by the orbital limit when the field is applied perpendicular to the film surface. Figure 3(b) shows the thickness dependence of the critical temperature (top) and the critical field (bottom) at base temperature. While the 10 nm sample shows the highest T_c , the 5.5 nm, 7 nm and 10 nm samples show similar H_{c2} .

Discussion

To our knowledge, no superconducting transition has been reported in bulk or thin film WTe_2 at ambient pressure. When high hydrostatic pressure is applied to the crystal, several groups have reported pressure-induced superconductivity^{30,31}, in which H_{c2} does not show the large enhancement beyond the paramagnetic limit. However, while the lattice constant of the crystal shrinks under high pressure, the WTe_2 thin film experiences tensile strain and in-plane lattice expansion due to the larger lattice constant of the sapphire substrate, which is about 4.76 Å. Also, it has been reported that the pressure-induced superconductivity in WTe_2 is associated with the structural transition from a non-centrosymmetric T_d crystal structure to a centrosymmetric $1T'$ structure⁴².

We believe that something very different is occurring in our thin film samples, because X-ray scattering suggests that the crystal structure is in the non-centrosymmetric T_d phase, as shown in the supplement. This is in contrast with the case of WTe_2 films grown on Bi_2 and MoS_2 where $1T'$ phase was observed⁴³. If the system is in the non-centrosymmetric T_d phase, the high H_{c2}/H_p could be attributed to Ising type spin-orbit coupling.

We note that the electrical transport properties above T_c demonstrate that the epitaxially grown WTe_2 films have electron-type carriers and that they are a heavily doped two-dimensional electronic system with the strong spin-orbit coupling (see the supplement). The crystal structure of our thin films implies that they have the same electronic structure as bulk WTe_2 with tilted Weyl fermions. However, photoemission studies would reveal directly the energy dispersion in our MBE thin films. Our result calls for detailed tunneling and photoemission on this new family of the TMD superconducting films.

The most exciting observation is the magnetic-field-enhanced and non-monotonic superconductivity in our WTe_2 thin films. One possible explanation is the Ising superconductivity in which the breaking of inversion symmetry predicts a non-monotonic H_{c2} vs. T trend near the ground state. As shown in the supplement, the competition of valley-degeneracy, the Rashba interaction, and magnetic Zeeman energy not only leads to H_{c2} much larger than the paramagnetic Pauli limit, but also leads to non-monotonic T dependence of H_{c2} . However, also note that the simple fitting including the competition of Rashba and Zeeman terms does not explain our results as shown in the supplement.

Indeed, however, since our samples are very thin and have lattice mismatch between the film and the substrate, it is difficult to exactly determine if the samples are non-centrosymmetric or not. Thus, further experiments are necessary to confirm if the exotic non-monotonic behavior of H_{c2} as well as extremely high H_{c2}/H_p are related to the symmetry. These experiments may further help determine the implication of the pairing symmetry. If the sample is centrosymmetric and in the $1T'$ phase, high H_{c2}/H_p might arise from the p-wave pairing. We note further that even in the centrosymmetric $1T'$ bulk phase, the thin film is still non-centrosymmetric when an odd number of atomic layers are grown.

The other possibility is that finite-momentum pairing theoretically predicts a non-monotonic $H_{c2\parallel ab} - T$ trace³, an interesting state where the in-plane magnetic field enhances T_c . This exotic pairing state may be enabled in WTe_2 by inversion symmetry breaking and the novel type-II Weyl semimetal electronic state in WTe_2 . We note that generally this may lead to the magnetic field enhancement both near the ground state and near the zero-field superconducting transition at T_{c0} .

In summary, we resolved unconventional superconducting behaviors of MBE grown WTe_2 thin films. We observed a 1.6% enhancement of T_c by magnetic field, non-monotonic H_{c2} vs T_c in the zero temperature limit, and an H_{c2} more than 10 times larger than the Pauli limit H_p . These results not only support the existence of Ising superconductivity, but also indicate further unconventional properties.

Methods

Thin film growth. WTe_2 thin films were grown on a sapphire substrate using a Veeco Genxplor MBE system. Prior to loading into the MBE chamber, the c -plane sapphire substrates were first cleaned using acetone, methanol, and deionized water. The sapphire was subsequently cleaned at elevated temperatures in the MBE chamber prior to growth initiation. During the growth of WTe_2 , the substrate temperature was $\sim 350^\circ$. A PBN (Pyrolytic Boron Nitride) effusion cell and an e-beam evaporator were used for the thermal evaporation of Te and W, respectively. The Te flux was measured to be $\sim 5 \times 10^{-8}$ torr. The growth rate was estimated to be ~ 1.2 Å/min. A very slow deposition rate is used to reduce the formation of Te vacancies, which has been commonly observed for transition metal telluride materials⁴⁴.

Scanning probe microscopy. The surface morphology of as-grown WTe_2 films were determined by scanning probe microscopy (SPM, Bruker MultiMode) using the tapping mode under ambient conditions. The probe was coated with Cr/Pt thin film with a force constant of 40 N/m, and the tip radius was less than 25 nm.

X-ray photoelectron spectroscopy. X-ray photoelectron spectroscopy (XPS, Thermo Sci.) was employed to investigate the element components, bonding structure, and surface stability of WTe_2 thin films. The X-ray source is $\text{Al-K}\alpha$ and has a spot size of 400 μm . Survey scans were performed from 0 to 1350 eV for the binding energy, and core-level scans were from 235 to 270 eV for W 4d and from 560 to 600 eV for Te 3d, respectively.

Transmission electron microscopy. High-resolution transmission electron microscopy (HR-TEM, JEOL 2100 F) revealed cross-sectional atomic structure of WTe_2 thin films, and the element distribution was studied

using an energy dispersive X-ray spectroscopy (EDX, Oxford Ins, AZtec). The specimen was prepared using focused ion beam (FIB) technique (Hitachi, FB2000A) with a titanium protection layer on the top surface. This preparation method made WTe_2 films intact, preserved the surface morphology, and revealed the interface heterostructure between WTe_2 and sapphire.

X-ray Diffraction. Crystal structures of MBE-grown WTe_2 thin films were analyzed by X-ray diffraction (XRD, Bruker D8 Advance) in the Bragg-Brentano geometry. The X-ray source is $\text{Cu-K}\alpha$ with a wavelength of 1.542 Å. Diffraction spectra were collected from 10° to 80° (2theta) with a step size of 0.02° .

Electrical transport characterization. The resistance of WTe_2 thin films was measured by standard four-probe measurement in Oxford Instruments Triton 200, Quantum Design PPMS and National High Magnetic Field Laboratory (NHMFL) using Keithley 6221 AC current source (typically around 13 Hz) and Stanford Research SR830 lock-in amplifier. In NHMFL, high magnetic fields up to 35 T were applied by the resistive magnet. Small enough excitation of current was applied so that we can ignore the effect of heating or H_{c2} suppression. The current dependence of voltage is obtained by the combination of Keithley 6221 and 2182 A. The critical temperature of superconducting transition T_c is defined as $R(T_c) = 0.5R(T = 4\text{K})$. As the magnetoresistance becomes saturated at high fields, critical field H_{c2} is defined as well by $R(H_{c2}) = 0.5R_{\text{sat}}$, where R_{sat} is the saturated resistance. Critical current I_c is determined as $R(I = I_c) = 0.5R(I = 1\text{mA})$ obtained from the I-V curves.

References

1. Tinkham, M. *Introduction to superconductivity* (Courier Corporation, 1996).
2. Jeffrey Gardner, H. *et al.* Enhancement of superconductivity by a parallel magnetic field in two-dimensional superconductors. *Nat Phys* **7**, 895–900, <https://doi.org/10.1038/nphys2075> (2011).
3. Michaeli, K., Potter, A. C. & Lee, P. A. Superconducting and Ferromagnetic Phases in $\text{SrTiO}_3/\text{LaAlO}_3$ Oxide Interface Structures: Possibility of Finite Momentum Pairing. *Phys. Rev. Lett.* **108**, 117003, <https://doi.org/10.1103/PhysRevLett.108.117003> (2012).
4. Kaur, R. P., Agterberg, D. F. & Sigrist, M. Helical Vortex Phase in the Noncentrosymmetric CePt_3Si . *Phys. Rev. Lett.* **94**, 137002, <https://doi.org/10.1103/PhysRevLett.94.137002> (2005).
5. Nagai, Y., Hoshino, S. & Ota, Y. Critical temperature enhancement of topological superconductors: A dynamical mean-field study. *Phys. Rev. B* **93**, 220505, <https://doi.org/10.1103/PhysRevB.93.220505> (2016).
6. Lu, J. *et al.* Evidence for two-dimensional Ising superconductivity in gated MoS_2 . *Science* **350**, 1353–1357 (2015).
7. Geim, A. K. & Grigorieva, I. V. Van der Waals heterostructures. *Nature* **499**, 419–425 (2013).
8. Ross, J. S. *et al.* Electrically tunable excitonic light-emitting diodes based on monolayer WSe_2 pn junctions. *Nature nanotechnology* **9**, 268–272 (2014).
9. Wu, S. *et al.* Monolayer semiconductor nanocavity lasers with ultralow thresholds. *Nature* **520**, 69–72 (2015).
10. Bernardi, M., Palummo, M. & Grossman, J. C. Extraordinary sunlight absorption and one nanometer thick photovoltaics using two-dimensional monolayer materials. *Nano letters* **13**, 3664–3670 (2013).
11. Lopez-Sanchez, O., Lembke, D., Kayci, M., Radenovic, A. & Kis, A. Ultrasensitive photodetectors based on monolayer MoS_2 . *Nature nanotechnology* **8**, 497–501 (2013).
12. Xiao, D., Liu, G.-B., Feng, W., Xu, X. & Yao, W. Coupled spin and valley physics in monolayers of MoS_2 and other group-VI dichalcogenides. *Physical Review Letters* **108**, 196802 (2012).
13. Jones, A. M. *et al.* Optical generation of excitonic valley coherence in monolayer WSe_2 . *Nature nanotechnology* **8**, 634–638 (2013).
14. Jariwala, D., Sangwan, V. K., Lauhon, L. J., Marks, T. J. & Hersam, M. C. Emerging device applications for semiconducting two-dimensional transition metal dichalcogenides. *ACS nano* **8**, 1102–1120 (2014).
15. Ugeda, M. M. *et al.* Characterization of collective ground states in single-layer NbSe_2 . *Nature Physics* **12**, 92–97 (2016).
16. Tsen, A. W. *et al.* Nature of the quantum metal in a two-dimensional crystalline superconductor. *Nat Phys* **12**, 208–212, <https://doi.org/10.1038/nphys3579> (2016).
17. Saito, Y. *et al.* Superconductivity protected by spin-valley locking in ion-gated MoS_2 . *Nat Phys* **12**, 144–149, <https://doi.org/10.1038/nphys3580> (2016).
18. Xi, X. *et al.* Ising pairing in superconducting NbSe_2 atomic layers. *Nature Physics* **12**, 139–143 (2016).
19. Xi, X. *et al.* Strongly enhanced charge-density-wave order in monolayer NbSe_2 . *Nat Nano* **10**, 765–769, <https://doi.org/10.1038/nnano.2015.143> (2015).
20. Qian, X., Liu, J., Fu, L. & Li, J. Quantum spin Hall effect in two-dimensional transition metal dichalcogenides. *Science* **346**, 1344–1347 (2014).
21. Soluyanov, A. A. *et al.* Type-II Weyl semimetals. *Nature* **527**, 495–498 (2015).
22. Belopolski, I. *et al.* Fermi arc electronic structure and Chern numbers in the type-II Weyl semimetal candidate $\text{Mo}_x\text{W}_{1-x}\text{Te}_2$. *Phys. Rev. B* **94**, 085127, <https://doi.org/10.1103/PhysRevB.94.085127> (2016).
23. Wu, Y. *et al.* Observation of Fermi arcs in the type-II Weyl semimetal candidate WTe_2 . *Phys. Rev. B* **94**, 121113, <https://doi.org/10.1103/PhysRevB.94.121113> (2016).
24. Wang, C. *et al.* Observation of Fermi arc and its connection with bulk states in the candidate type-II Weyl semimetal WTe_2 . *Phys. Rev. B* **94**, 241119, <https://doi.org/10.1103/PhysRevB.94.241119> (2016).
25. Liang, A. *et al.* Electronic Evidence for Type II Weyl Semimetal State in MoTe_2 . *arXiv preprint arXiv:1604.01706* (2016).
26. Jiang, J. *et al.* Signature of type-II Weyl semimetal phase in MoTe_2 . *Nature Communications* **8**, 13973 EP – <https://doi.org/10.1038/ncomms13973> (2017).
27. Deng, K. *et al.* Experimental observation of topological Fermi arcs in type-II Weyl semimetal MoTe_2 . *Nat Phys* **12**, 1105–1110, <https://doi.org/10.1038/nphys3871> (2016).
28. Huang, L. *et al.* Spectroscopic evidence for a type II Weyl semimetallic state in MoTe_2 . *Nat Mater* **15**, 1155–1160, <https://doi.org/10.1038/nmat4685> (2016).
29. Ali, M. N. *et al.* Large, non-saturating magnetoresistance in WTe_2 . *Nature* **514**, 205–208, <https://doi.org/10.1038/nature13763> (2014).
30. Pan, X.-C. *et al.* Pressure-driven dome-shaped superconductivity and electronic structural evolution in tungsten ditelluride. *Nature communications* **6** (2015).
31. Kang, D. *et al.* Superconductivity emerging from a suppressed large magnetoresistant state in tungsten ditelluride. *Nature communications* **6** (2015).
32. Qi, Y. *et al.* Superconductivity in Weyl semimetal candidate MoTe_2 . *Nature Communications* **7**, 11038 EP – <https://doi.org/10.1038/ncomms11038> (2016).
33. Kang, K. *et al.* High-mobility three-atom-thick semiconducting films with wafer-scale homogeneity. *Nature* **520**, 656–660 (2015).
34. Zhang, Y. *et al.* Direct observation of the transition from indirect to direct bandgap in atomically thin epitaxial MoSe_2 . *Nature nanotechnology* **9**, 111–115 (2014).

35. Roy, A. *et al.* Structural and Electrical Properties of MoTe₂ and MoSe₂ Grown by Molecular Beam Epitaxy. *ACS applied materials & interfaces* **8**, 7396–7402 (2016).
36. Xenogiannopoulou, E. *et al.* High-quality, large-area MoSe₂ and MoSe₂/Bi₂Se₃ heterostructures on AlN (0001)/Si (111) substrates by molecular beam epitaxy. *Nanoscale* **7**, 7896–7905 (2015).
37. Vishwanath, S. *et al.* Controllable growth of layered selenide and telluride heterostructures and superlattices using molecular beam epitaxy. *Journal of Materials Research* 1–11 (2016).
38. Lee, C.-H. *et al.* Tungsten Ditelluride: a layered semimetal. *Scientific reports* **5** (2015).
39. Clogston, A. M. Upper limit for the critical field in hard superconductors. *Physical Review Letters* **9**, 266 (1962).
40. Chandrasekhar, B. A note on the maximum critical field of high-field superconductors. *Applied Physics Letters* **1**, 7–8 (1962).
41. Pippard, A. B. *Magnetoresistance in metals*, vol. 2 (Cambridge University Press, 1989).
42. Lu, P. *et al.* Origin of superconductivity in the Weyl semimetal WTe₂ under pressure. *Physical Review B* **94**, 224512 (2016).
43. Walsh, L. A. *et al.* WTe₂ thin films grown by beam-interrupted molecular beam epitaxy. *2D Materials* **4**, 025044 (2017).
44. Collins-McIntyre, L. *et al.* Growth of Bi₂Se₃ and Bi₂Te₃ on amorphous fused silica by MBE. *physica status solidi (b)* **252**, 1334–1338 (2015).

Acknowledgements

We would like to thank the helpful discussion with Liang Fu. This work is mainly supported by the National Science Foundation (NSF) Center for Photonic and Multiscale Nanomaterials DMR 1120923 (electrical transport characterization in superconducting magnets) and by the Natural Sciences and Engineering Research Council of Canada (NSERC) and US Army Research Office under the grant W911NF-16-1-0310 (sample growth) and by NSF award DMR 1707620 (mutual inductance and Meissner effect characterization). Supporting measurements were made possible with the support by the Department of Energy under Award No. DE-SC0008110 (measurement in intense DC magnetic field above 14 T), by the National Science Foundation under Award No. ECCS-1307744 (device fabrications), by the Office of Naval Research through the Young Investigator Prize under Award No. N00014-15-1-2382 (supporting magnetization and magnetic susceptibility measurements) and the National Science Foundation Major Research Instrumentation award under No. DMR-1428226 (supports the equipment for the magnetization and electrical transport characterizations). Some experiments were performed at the National High Magnetic Field Laboratory, which is supported by NSF Cooperative Agreement No. DMR-1157490, by the State of Florida, and by the DOE. We are grateful for the assistance of Tim Murphy, Glover Jones, and Ju-Hyun Park of NHMFL. T.A. thanks the Nakajima Foundation for support. B.J.L. acknowledges support by the National Science Foundation Graduate Research Fellowship under Grant No. F031543. Y.L. is grateful to the KSAS General Fund Start-up at Johns Hopkins.

Author Contributions

L.L. and Z.M. designed the experiments. T.A. designed and performed the transport experiment, analyzed data and prepared the manuscript assisted by G.L., B.L., L.C. and C.T., Y.W. and Z.M. fabricated the WTe₂ film samples and led the sample characterization assisted by S.Z. and D.L. All authors discussed the results and commented on the manuscript.

Additional Information

Supplementary information accompanies this paper at <https://doi.org/10.1038/s41598-018-24736-x>.

Competing Interests: The authors declare no competing interests.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2018